
**“EFFECTS OF A FLUORIDE CONTAINING CASEIN
PHOSPHOPEPTIDE-AMORPHOUS CALCIUM PHOSPHATE
COMPLEX ON SHEAR BOND STRENGTH AND ADHESIVE
REMNANT INDEX OF TEETH ERODED BY DIFFERENT
BEVERAGES: AN IN-VITRO STUDY”**

By

Dr. ANN BENZY

Reg. No. II0218001

Dissertation

Submitted to

KAHER, Belagavi, Karnataka

In partial fulfillment of the requirements for the degree of

**MASTER OF DENTAL SURGERY
IN
ORTHODONTICS AND DENTOFACIAL
ORTHOPAEDICS
(BRANCH – V)**

Under the Guidance Of

Dr. ROHAN S. HATTARKI M.D.S

**DEPARTMENT OF
ORTHODONTICS AND DENTOFACIAL ORTHOPAEDICS
KLE VISHWANATH KATTI INSTITUTE OF DENTAL SCIENCES,
KAHER, BELAGAVI, KARNATAKA.**

2018-2021

KAHER, BELAGAVI

Declaration by the Candidate

I hereby declare that this dissertation/thesis entitled “**EFFECTS OF A FLUORIDE CONTAINING CASEIN PHOSPHOPEPTIDE-AMORPHOUS CALCIUM PHOSPHATE COMPLEX ON SHEAR BOND STRENGTH AND ADHESIVE REMNANT INDEX OF TEETH ERODED BY DIFFERENT BEVERAGES: AN IN-VITRO STUDY**” is a bonafide and genuine research work carried out by me under the guidance of **Dr. ROHAN S. HATTARKI** M.D.S, Reader, Department of Orthodontics and Dentofacial Orthopaedics, KLE Vishwanath Katti Institute of Dental Sciences, KAHER, Belagavi-590010.

Date:

Dr. ANN BENZY

Place: Belagavi

KAHER, BELAGAVI

Certificate by Guide

This is to certify that the dissertation entitled “**EFFECTS OF A FLUORIDE CONTAINING CASEIN PHOSPHOPEPTIDE-AMORPHOUS CALCIUM PHOSPHATE COMPLEX ON SHEAR BOND STRENGTH AND ADHESIVE REMNANT INDEX OF TEETH ERODED BY DIFFERENT BEVERAGES: AN IN-VITRO STUDY**” is a bonafide research work done by **Dr. ANN BENZY**, postgraduate student in partial fulfillment of the requirement for the degree of **Master of Dental Surgery (MDS)** in Orthodontics and Dentofacial Orthopaedics, (Branch V).

Date:

Place: Belagavi

Dr. ROHAN S. HATTARKI_{M.D.S.}

Reader,

Department of Orthodontics &

Dentofacial Orthopaedics,

KLE Vishwanath Katti

Institute of Dental Sciences,

KAHER,

Belagavi-590010.

KAHER, BELAGAVI

**Endorsement by the Head of the Department and
Principal/Head of the Institution**

This is to certify that the dissertation entitled “**EFFECTS OF A FLUORIDE CONTAINING CASEIN PHOSPHOPEPTIDE-AMORPHOUS CALCIUM PHOSPHATE COMPLEX ON SHEAR BOND STRENGTH AND ADHESIVE REMNANT INDEX OF TEETH ERODED BY DIFFERENT BEVERAGES: AN IN-VITRO STUDY**” is a bonafide research work done by **Dr. ANN BENZY**, postgraduate student under the guidance of **Dr. ROHAN S. HATTARKI_{M.D.S.}**, Reader, Department of Orthodontics and Dentofacial Orthopaedics, KAHER’S KLE Vishwanath Katti Institute of Dental Sciences, Belagavi-590010.

Head of Department

Dr. Tejashri Pradhan M. D.S.
Professor & Head,
Department of Orthodontics and
Dentofacial Orthopaedics,
KLE Vishwanath Katti
Institute of Dental Sciences,
KAHER, Belagavi.

Date:
Place: Belagavi

Principal

Dr. Alka Kale M. D.S.
Principal,
KLE Vishwanath Katti
Institute of Dental Sciences,
KAHER, Belagavi.

Date:
Place: Belagavi

KAHER, BELAGAVI

Copyright

Declaration by the Candidate

I hereby declare that the KLE University, Belagavi, Karnataka shall have the rights to preserve, use & disseminate this Dissertation/Thesis entitled **“EFFECTS OF A FLUORIDE CONTAINING CASEIN PHOSPHOPEPTIDE-AMORPHOUS CALCIUM PHOSPHATE COMPLEX ON SHEAR BOND STRENGTH AND ADHESIVE REMNANT INDEX OF TEETH ERODED BY DIFFERENT BEVERAGES: AN IN-VITRO STUDY”** in print or electronic format for Academic/Research Purposes.

Date:

Place: Belagavi

Dr. ANN BENZY

© KAHER, Belagavi Karnataka

[Established under section 3 of the UGC Act, 1956 vide GOI. Notification No. F.9-19/2000- U.3 (A)]

UNDERTAKING

I, **Dr. ANN BENZY**, Post-Graduate student in the subject of Orthodontics have completed research work on the topic **“EFFECTS OF A FLUORIDE CONTAINING CASEIN PHOSPHOPEPTIDE-AMORPHOUS CALCIUM PHOSPHATE COMPLEX ON SHEAR BOND STRENGTH AND ADHESIVE REMNANT INDEX OF TEETH ERODED BY DIFFERENT BEVERAGES: AN IN-VITRO STUDY”**, in the year 2021.

I have been given to understand that any research work I undertake for the purpose of the dissertation, oral presentation, or publication during my study course shall be the property of the KLE VK Institute of Dental Sciences, KAHER, Belagavi. Hence, I hereby declare that the name of the Department Institute and University shall be mentioned in my publications. The authorship shall be according to the guideline informed to me.

Signature of the Post-Graduate Student

PLAGIARISM CHECK REPORT

Scientific Correspondence and Review Committee



KLE VK Institute of Dental Sciences
A Constituent Unit of KLE Academy of Higher Education and Research
(Deemed-to-be-University u/s 3 of the UGC Act, 1956)
Nehru Nagar, Belagavi - 590 010, Karnataka State

Accredited 'A' Grade by NAAC (2nd Cycle)
☎: 0831-2470362
FAX: 0831-2470640

Placed in Category 'A' by MHRD (GoI)
Web: <http://www.kledental-bgm.edu.in>
E-mail: principal@kledental-bgm.edu.in

Date :

Serial No. : **034**

PLAGIARISM CHECK REPORT

Name of the Applicant : *Dr. Ann Benzly*
UG / PG / Ph.D / Staff : *post graduate*
Batch & Year : *2018 - 2021*
Department : *Department of Orthodontics.*

The soft copy of Research Work / Manuscript by *Dr. Ann Benzly*..... entitled
"*Effects of fluoride containing casein phosphopeptide -
amorphous calcium phosphate complex on shear bond strength
and adhesive remnant index of teeth eroded by different beverages: An in-vitro study*"
under the guidance ofhas been submitted for

Anti-Plagiarism check to the Scientific Correspondence & Review Committee of KLE VK
Institute of Dental Sciences using "Turn-it-in" software.

The scan has been carried out and the scanned output reveals a Similarity Index of
2.....%, which is **within / not within** the acceptable limits of 10% as per
the UGC guidelines.


Member Secretary
Scientific Correspondence and Review Committee
KLEVK Institute of Dental Sciences
KAHER-Belagavi


Chairman
Scientific Correspondence and Review Committee
KLEVK Institute of Dental Sciences
KAHER - Belagavi

UNDERTAKING

I, **Dr. ANN BENZY** hereby declare that the information and data mentioned in my thesis entitled **“EFFECTS OF A FLUORIDE CONTAINING CASEIN PHOSPHOPEPTIDE-AMORPHOUS CALCIUM PHOSPHATE COMPLEX ON SHEAR BOND STRENGTH AND ADHESIVE REMNANT INDEX OF TEETH ERODED BY DIFFERENT BEVERAGES.: AN IN-VITRO STUDY”** belongs to me and is original.

I am aware of the definition of plagiarism as detailed below:

- An act or instance of using or closely imitating the language and thoughts of another author without authorization and the representation of that author’s work as one’s own, as by not crediting the original author.
- A piece of writing or other work reflecting such unauthorized use or imitation.
- The deliberate or reckless representation of another’s words, thoughts, or ideas as one’s own without attribution in connection with the submission of academic work, whether graded or otherwise.

I hereby declare that the thesis prepared by me is the original one and does not involve plagiarism anywhere. In case at a later stage it is found that I have indulged in plagiarism, then I am solely responsible for the same and the Institution is at liberty to take any disciplinary action against me including cancellation of the dissertation or any other penalties imposed by the University.

Signature of Student
Place:
Date:

Signature of Guide
Place:
Date:

BIostatISTICS CLEARANCE CERTIFICATE



KLE V.K. Institute of Dental Sciences

(A Constituent unit of KLE Academy of Higher Education & Research
Deemed-to-be-University u/s 3 of the UGC Act, 1956)
Nehru Nagar, Belagavi-590 010 INDIA

Re-Accredited 'A' grade by NAAC (2nd Cycle) & Placed in Category 'A' by MHRD (GoI)

• 0831-2470362
FAX: 0831-2470640

Web: <http://www.kledental-bgm.edu.in>
E-mail: principal@kledental-bgm.edu.in




Biostatistics Clearance Certificate

This is to certify that the Biostatistics aspect of the Dissertation / Research work of...Dr.Ann Benzy.....

Entitled "Effects of a fluoride containing casein phosphopeptide-amorphous calcium phosphate complex on shear bond strength and adhesive remnant index of teeth eroded by different beverages. :An In-Vitro Study" has been done under my guidance and considered satisfactory.

Place : Belagavi
Date :21.09.2020

Dr. Ravi Shirahatti
MDS(Public Health Dentistry)
PG Diploma(Bio-Statistics)
Name & Signature of Biostatistician

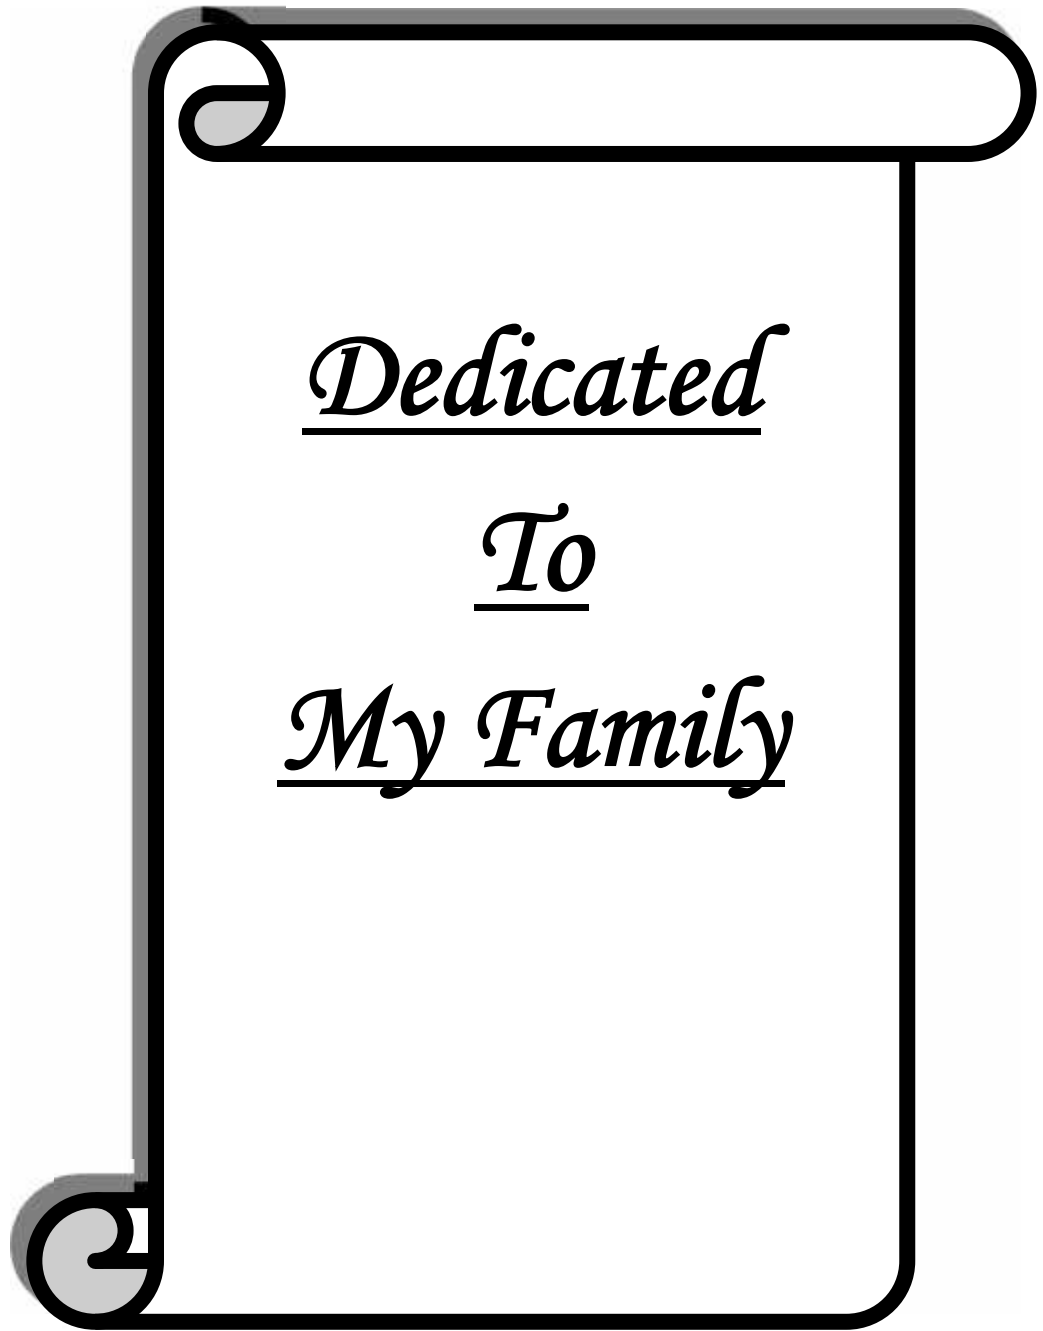

ACKNOWLEDGEMENT

I would like to begin by thanking God for giving me the strength, knowledge, ability and opportunity to undertake this research study and to persevere and complete it satisfactorily. Without his blessings, this achievement would not have been possible.

I present this thesis as an ode to all the qualities and principles, which have been instilled in me by all those who have enriched my life through their knowledge and wisdom.

My profound respect, deep sense of gratitude and indebtedness to my respected teacher and guide **Dr.Rohan S.Hattarki** MDS, Reader, Department of Orthodontics and Dentofacial Orthopaedics, KAHER's KLE Vishwanath Katti Institute of Dental Sciences, KLE University, Belagavi for his heartfelt support at all times. He has provided me with invaluable guidance, inspiration and suggestions, he has given me all the liberty to pursue my research, while silently and unobtrusively ensuring that I stay on course and do not drift away from the core of my research. I gratefully acknowledge the suggestions and advice given to me by him through my time as a post graduate student. His passion for the subject, meticulousness and attention to detail, vast knowledge, calm and composed nature and skill are all standards I really hope to achieve someday. Without his able guidance, patience and faith in my abilities, it would not have been possible for me to complete this dissertation.

I am immensely indebted to **Dr. ALKA KALE** MDS Principal, KLE Vishwanath Katti Institute of Dental Sciences, KAHER, Belagavi, for providing the required facilities and infrastructure.

I am privileged to express my extreme gratefulness to my respected teacher **Dr. Tejashri Pradhan.** MDS, Professor, and Head, Faculty of Dentistry, Department of Orthodontics and Dentofacial Orthopaedics, KLE Vishwanath Katti Institute of Dental Sciences, KAHER, Belagavi for her willingness to always render help when needed and for her wise counsel.

I am greatly indebted to my respected teachers **Dr. K.M. Keluskar** MDS, PhD, Professor, **Dr. Roopa Jatti** MDS, Professor, **Dr. Anand Badavannavar** MDS Reader, **Dr. Amit** MDS, **Dr. Trupti** MDS, **Dr. Devyani** MDS and **Dr. Adithi** MDS, Senior Lecturers, for their guidance and support at all times.

A special thanks to **Dr. Fifi, Dr. Akin, Dr. Rujuta and Dr. Riddhi** for all their help, valuable inputs and insight which helped me complete this study without any glitches.

I would like to take this opportunity to also thank **Dr. Prithvick** and **Dr. Prashasti** who has been like my family away from home, always standing by me through my highs and lows, been my pillar of strength, and has seen me grow as a person during the course of my post-graduation.

I sincerely thank my postgraduate colleagues, **Dr. Susmita, Dr. Pooja, Dr. Yatin, Dr. Poojit and Dr. Aaati** for their modest help, words of encouragement and confidence which kept me motivated.

I would like to thank my seniors **Dr. Fifi, Dr. Sumedh, Dr. Annie, Dr. Rujuta, Dr. Ana, Dr. Shreya, Dr.Pravin and Dr.Parthiban** for their constant support and motivation that helped me to do my work with maximum enthusiasm.

I would also like to thank all my juniors **Dr.Akin, Dr. Charles, Dr. Deepa, Dr. Pranavi, Dr.Preethi , Dr. Sanjyot, Dr.Riddhi, Dr. Shreya, Dr. Namit, Dr. Tanvi, Dr. Aravindsamy, and Dr. Sagar** for their timely assistance whenever needed.

I would like to extend my sincere thanks to Mr. Mahantesh, Mr. Raju, Mr. Bringi and all the non-teaching staff.

I would like to acknowledge the work of **Dr. Ravi Shirahatti** for helping me in statistical analysis of the data obtained through this study.

I would like to acknowledge the tireless work of **Mr. Anand** and **Mr. Arun** of **Shri Vighneshwara Associates** Computers of J.N.M.C for excellent data processing and completion of this dissertation.

I would like to acknowledge those who are the core of my life—**my family**, who have laid the foundation stone of fundamental principles and morals which have made me the person I am today, **and my friends** especially **Ms.Annie** for their constant encouragement, support and guidance, and for being a firm backbone to my life through my many trials and tribulations.

Dr. Ann Benzy

LIST OF ABBREVIATIONS

SBS	SHEAR BOND STRENGTH
AEP	ACQUIRED ENAMEL PELLICLE
UTM	UNIVERSAL TESTING MACHINE
CPP-ACP	CASEIN PHOSPHOPEPTIDE- AMORPHOUS CALCIUM PHOSPHATE
CPP-ACPF	CASEIN PHOSPHOPEPTIDE- AMORPHOUS CALCIUM PHOSPHATE FLUORIDE
LED	LIGHT EMITTING DIODE
ARI	ADHESIVE REMNANT INDEX

ABSTRACT

INTRODUCTION-

One of the most commonly encountered complications that we come across during orthodontic treatment is loosening of brackets or bond failure. Dental erosion and loss of tooth structure have also been reported to reduce bond strength and cause bond failure. The frequency of dental erosion in the recent past has increased because of the increase in consumption of various acidic drinks and it has been reported to reduce the shear bond strength. Use of various remineralization agents have shown to increase enamel surface hardness post-dental erosion and it has been suggested as a prophylactic agent.

AIM-

- To evaluate the effects of “CPP-ACPF (casein phosphopeptide-amorphous calcium phosphate with fluoride)”, a remineralization agent on shear bond strength and adhesive remnant index of teeth, eroded by different beverages namely Coca-Cola and Lipton lemon flavoured ice tea

MATERIALS AND METHODS-

Fifty-two maxillary/mandibular premolars were chosen and allocated into four groups with 13 teeth in each with respect to beverage used for erosion and enamel pre-treatment: A1(Eroded by Coca-Cola: Pre-treatment with “CPP-ACPF”). A2(Eroded by Coca-Cola, no enamel Pre-treatment). B1(Eroded by Lipton lemon flavoured ice tea: Pre-treatment with “CPP-ACPF”). B2(Eroded by Lipton lemon flavoured ice tea: No pre-treatment). The specimens were then bonded and subjected to shear bond strength

test. “The remaining adhesive on the teeth were assessed after debonding with Modified Adhesive Remnant Index (ARI)”. Data evaluation was done by Kruskal Wallis Chi-Square test.

RESULTS AND CONCLUSIONS-

1. Application of remineralization agents like “CPP-ACPF” on teeth eroded by aerated soft drinks, increased the median shear bond strength.
2. “CPP-ACPF” pre-treatment did not affect the SBS of teeth eroded by Lipton lemon flavoured ice tea.
3. Irrespective of the acidic beverage used for erosion, or the enamel pre-treatment with “CPP-ACPF”, statistically significant difference was not seen in the SBS between the groups which suggest the need for further clinical studies to find the effectiveness of the remineralization procedure.
4. Bond failure of brackets in all the groups were at enamel-adhesive interface leaving some residue on the enamel surface.

CONTENTS

SL.NO.	PARTICULARS	PAGE NO.
1	INTRODUCTION	1-3
2	AIM & OBJECTIVES	4
3	REVIEW OF LITERATURE	5-9
4	MATERIALS AND METHOD	10-22
5	RESULTS	23-26
6	DISCUSSION	27-31
7	LIMITATIONS OF THE STUDY	32
8	CONCLUSION	33
9	SUMMARY	34
10	BIBLIOGRAPHY	35-40
11	ANNEXURE	41-43

LIST OF TABLES

TABLE NO.	PARTICULARS	PAGE NO.
1.	GROUPING OF SAMPLES USED IN THE STUDY	24
2.	COMPARISON BETWEEN THE GROUPS FOR SHEAR BOND STRENGTH	25
3.	COMPARISON BETWEEN THE GROUPS FOR ADHESIVE REMANT INDEX (ARI)	26

LIST OF GRAPHS

GRAPH NO.	PARTICULARS	PAGE NO.
1.	BAR GRAPH SHOWING MEDIAN SHEAR BOND STRENGTH IN MEGA PASCALS FOR THE GROUPS	25
2.	BAR GRAPH SHOWING MEDIAN ARI FOR THE GROUPS	26

LIST OF IMAGES

PHOTOGRAPH NO.	PARTICULARS	PAGE NO.
1.	GROUP A1 SAMPLES BEVERAGE:COCA-COLA, CPP-ACPF TREATED	17
2.	GROUP A2 SAMPLES BEVERAGE:COCA-COLA, NO PRE-TREATMENT	17
3.	GROUP B1 BEVERAGE:LIPTON LEMON FLAVOURED ICE TEA, CPP-ACPF TREATED	18
4.	GROUP B2 SAMPLES BEVERAGE:LIPTON LEMON FLAVOURED ICE TEA, NO PRE-TREATMENT	18
5.	MATERIALS USED	19
6.	BEVERAGES USED FOR CONDITIONING TEETH	19
7.	UNIVERSAL TESTING MACHINE	20
8.	SAMPLE SUBJECTED TO LOAD TO MEASURE THE SHEAR BOND STRENGTH	21

9.	CLOSE-UP VIEW OF A SAMPLE BEING SUBJECTED TO THE MAXIMUM LOAD FOR MEASURING SHEAR BOND STRENGTH	21
10.	SAMPLES EVALUATED UNDER STEREOMICROSCOPE TO MEASURE ARI	22

LIST OF ANNEXURES

S. NO.	PARTICULARS	PAGE NO.
1.	ETHICAL CLEARANCE CERTIFICATE	41
6.	DATA ENTRY SHEET	42-43

INTRODUCTION

One of the most commonly encountered complications that we come across during orthodontic treatment is loosening of brackets or bond failure. Bond failure rate should be minimized as replacing loose brackets is inefficient, time-consuming, and costly. The frequency of this has been found to vary between “0.5 and 17.6 percent”.^[1] Numerous causes can lead to loosening of brackets which includes “poor operator technique, variation in the enamel surface, saliva contamination, bracket properties, masticatory forces, and patient behavior”.^[1] Dental erosion and loss of tooth structure have also been reported to reduce bond strength and cause bond failure.

Recurring exposure of teeth to acidic medium together with functional and parafunctional forces causes dental erosion. Any acidic substance in the oral cavity has to initially pass through the acquired enamel pellicle (AEP). “The AEP is a thin acellular biofilm composed of proteins, enzymes, glycoproteins, carbohydrates and lipids” and it acts as a protective layer. “Once the acid passes through the AEP, its hydrogen ions (H⁺) starts breaking down the enamel crystals which leads to an initial demineralization indicated by a softening of the enamel and predisposing it to the effects of functional and parafunctional forces”.^[2]

Various drinks and food which are acidic or alcoholic can also be a major factor causing bond failure as they lead to dental erosion. Consumption of soft drinks which have low pH during orthodontic treatment decreases the SBS by reducing the hardness of the enamel around the brackets or composite resin disintegration.^[1]

Consumption of soft drinks and various types of tea has increased in the recent past. Aerated soft drinks and packed fruit juices are consumed more by children and adolescents and during adulthood, they shift to consumption of different types of tea like iced tea, herbal tea and green tea as they become more health-conscious.

“The term ‘soft’ drinks refers to all drinks except alcohol, mineral water, fruit juice, tea, coffee, or milk-based drinks, which may or may not be carbonated”.^[3] They are detrimental because of the elevated levels of sugar they carry and most of them are acidic in nature. “Frequently consumed soft drinks like Coca-Cola cause more dental erosion because they contain acids like phosphoric acid, citric and carbonic acid”. Phosphoric acid is more harmful as it is more acidic and causes more erosive lesions on the tooth surface.^[10]

“Although teas are known to be ‘safe’, most of these have high erosive potential because of their fruit products containing hydroxyl organic acids, such as citric, malic, and oxalic”. Few studies have reported dental erosion caused by tea.^[1] Most of these soft drinks and tea have a pH below the “critical limit for enamel demineralization (pH <5.5)” thus leading to erosive lesions on the tooth surface.^[3]

Dental erosion can be avoided by increasing the acid resistance of the tooth structure or by remineralization processes which requires calcium, phosphate and fluoride. “Casein phosphopeptide–amorphous calcium phosphate (CPP-ACP) which is derived from cow’s milk reduces the demineralization process of the enamel and enhances the remineralization process”. This is because casein, an amino acid, changes according to the pH. In low pH, “ACP” detaches from “CPP”, which elevates the “calcium and phosphate” levels in the saliva. The “CPP-ACP complexes” easily combine with the fluoride ions to form “CPP-ACPF”.^[5] “CPP-ACPF” acts as a

reservoir for fluoride as well as calcium and phosphate ions for remineralization. This “CPP-ACPF” complex, when added to “dentifrices, mouth rinses, chewing-gum, varnishes or sprays” delivers extra bioavailable calcium and phosphate ions. Demineralization caused by acidic and alcoholic drinks are reported to get reversed by these agents.

Even though studies have been done on soft drinks, tea, non-alcoholic beers etc. and it is proven to cause erosion and decrease in bond strength and it is also known that “CCP-ACPF” causes remineralization of teeth “for at least 2 weeks and limits demineralization up to 12 weeks”^[6], till date no study has been done to see if it improves the bond strength of eroded teeth. Adhesive remnant index (ARI) is used to determine the bond failure location whether it is adhesive bracket interface or adhesive tooth interface. Thus, this study sought to evaluate the effects of “CPP-ACPF” on bond strength and adhesive remnant index of teeth eroded by two different beverages namely Coca-Cola and Lipton lemon flavoured ice tea.

AIM OF THE STUDY

To evaluate the effects of “CPP-ACPF (casein phosphopeptide-amorphous calcium phosphate with fluoride)”, a remineralization agent on shear bond strength and adhesive remnant index of teeth, eroded by different beverages namely Coca-Cola and Lipton lemon flavoured ice tea

OBJECTIVES

- To evaluate the shear bond strength and adhesive remnant index of teeth eroded by Coca-Cola and treated with “CPP-ACPF” followed by bonding with Transbond XT and curing with LED curing gun
- To evaluate the shear bond strength and adhesive remnant index of teeth eroded by Lipton lemon flavoured ice tea and treated with “CPP-ACPF” followed by bonding with Transbond XT and curing with LED curing gun

REVIEW OF LITERATURE

K M Bishop (1999) explained various non carious lesions like “erosion, attrition and abrasion” and stated that they are part of a physiologic process that happens throughout life. He also described the causes and management which included dietary intake analysis and modification

Chan AS, Tran TTK, Hsu YH, Liu SYS, Kroon J (2020) did a systematic review on the effect of consumption of various beverages and food on dental erosion and concluded that it is a causative factor especially the consumption of carbonated drinks during the bedtime.

Hasheminejad N, Malek Mohammadi T, Mahmoodi MR, Barkam M1, Shahravan A (2020) conducted a cross-sectional study in Iranian adolescents and concluded that consumption of soft drinks was associated with an increase in dental caries and erosion

Rajeev G, Lewis AJ, N S (2020) did a study to see the effect of consumption of various beverages on teeth and he concluded that citric acid containing drinks have a low pH capable of causing dental erosion.

Ça rı Ulusoy, Arzu Müjdeci and Osman Gökay (2009) studied the effect of herbal teas and Coca-cola on the shear bond strength of orthodontic brackets and concluded that they had low pH and significantly reduced the shear bond strength.

Raúl Navarro, Ascensión Vicente, Antonio J. Ortiz and Luis A. Bravo (2011) studied “the effects of two soft drinks on bond strength and adhesive remnant on intact and sealed enamel and concluded that there was no significant difference among the groups”

Pasha A, Sindhu D, Nayak RS, Mamatha J, Chaitra KR, Vishwakarma S (2015) did an in-vitro study on the Effect of Two Soft Drinks(Mirinda and Coca-cola) on Shear Bond Strength and of intact and sealed Enamel and concluded that the two soft drinks significantly reduced the bond strength.

Casas-Apayco LC, Dreibi VM, Hipólito AC, Graeff MS4, Rios D, Magalhães AC, Buzalaf MA, Wang L (2014) did an in vitro study on erosive cola-based drinks and its effect on the bonding to enamel surface and concluded that they significantly reduced the bond strength.

Muratha Panich, Suchit Poolthong (2009) studied “the effect of casein phosphopeptide–amorphous calcium phosphate on enamel hardness of teeth eroded by cola drinks and concluded that the cola soft drink significantly decreased enamel hardness, “CPP-ACP” improved the hardness of eroded enamel”.

S. Burcak Cehreli et al (2012) studied the effects of a “fluoride containing casein phosphopeptide-amorphous calcium phosphate complex on the shear bond strength of orthodontic brackets and concluded that it did not compromise the bond strength”

Balakrishnan A et al (2013) evaluated caries remineralization potential of “Casein phosphopeptide - Amorphous calcium phosphate (CPP- ACP), 0.21% sodium fluoride - Tricalcium phosphate (f-TCP) and Calcium Sodium Phosphosilicate (CSP)” where they found that “CPP – ACP” showed better remineralizing potential compared to the other two agents.

Moufida Abufarwaa; Amal Noureldinb; Phillip M. Campbelle; Peter H. Buschangd (2019) studied the “longevity of casein phosphopeptide–amorphous calcium phosphate fluoride varnish’s preventative effects and concluded that CPP-

ACP fluoride varnish prevents enamel demineralization for at least 4 weeks and limits demineralization up to 12 weeks”.

Luiz Filipe Barbosa-Martins et al (2018) studied the effects of remineralization agents containing toothpaste like MI Paste™ and Curodont™ Repair on artificially demineralized dentin and concluded that they recovered the tensile bond strength, which was comparable to sound dentin.

Reynolds EC(1997) carried out an in-vitro study to examine the effects of “CPP-ACP” on demineralized lesions in third molar teeth. He found that it can maintain high concentration gradients of calcium and phosphate ions and ion pairs into the subsurface lesion, thus producing higher rates of enamel remineralization.

Jacob M. Tencate (1999) discussed the effects of fluoride and he concluded that remineralization was accelerated by fluoride.

Somani R, Jaidka S, Singh DJ, Arora V (2014) conducted a study on the remineralizing potential of various agents on dental erosion and concluded that “CPP-ACP with fluoride (Tooth Mousse Plus)” increased the post erosion microhardness of teeth more when compared to “CPP-ACP” without fluoride.

Kecik D, Cehreli SB, Sar C, Unver B (2008) studied the effect of “casein phosphopeptide-amorphous calcium phosphate(CPP-ACPF)”, on “the shear bond strength of brackets” and concluded that it can be used as a prophylaxis measure in fixed appliance therapy as it does not compromise bracket bond strength

Tabrizi A, Cakirer BA (2011) evaluated and compared “the effects of topical application of casein phosphopeptide- amorphous calcium phosphate(CPP-ACP) on the shear bond strength(SBS) of orthodontic brackets” which showed that “CPP-

ACP” can be used as a prophylactic agent before bonding of brackets, to reduce the risk of demineralization during the fixed orthodontic treatment.

Uyasal T, Baysal A, Uysal B, Aydmelge M, Al-Qunaian T (2011) compared the effect of “fluoride and casein phosphopeptide-amorphous calcium phosphate (CPP-ACP) containing topical agents on shear bond strength (SBS) and fracture failure mode of orthodontic brackets bonded to demineralized enamel”. It was concluded that the application of fluoride and “CPP-ACP gel” showed greater debonding forces than untreated demineralized samples.

Ekinzer A, Zorba YO, Uysal T, Ayrikcila S (2012) conducted a study to assess and compare the effects of different methods of inhibiting demineralization on the shear bond strength (SBS) and fracture mode of orthodontic adhesive on demineralized enamel surfaces. It was found that the tooth surfaces exposed to “CPP-ACPF” application showed higher debonding forces than the untreated, demineralized surfaces.

Soares R, De Ataide ID, Fernandes M, Lambor R. (2017) assessed the efficacy of four different remineralizing agents in which they concluded that “CPP-ACPF” had marginally better remineralization than Bioactive glass but without statistically significant difference.

Vidya Manoharan et al (2018) Evaluated the Remineralization Potential of “Casein Phosphopeptide- Amorphous Calcium Fluoride Phosphate and Novamin” on Artificially Demineralized Human Enamel in an in vitro study and concluded that even though both “CPP-ACPF” and Novamin showed remineralization potential, remineralization was found to be higher in the samples treated with “CPP-ACPF”.

Zeliha Mu" ge Baka; Mehmet Akin; Zehra Ileri; Faruk Ayhan Basciftci (2016) evaluated the effects of remineralization procedures using "casein phosphopeptide-amorphous calcium phosphate" on demineralized teeth and they concluded that it can restore the decreased SBS of orthodontic brackets and decrease surface roughness

Andrew P. Garry, Norah L. Flannigan(2017) investigated the remineralization of subsurface lesions of enamel treated with fluoride toothpaste (1450 ppm) or a combination of fluoride toothpaste and Tooth Mousse and they concluded that the combination had a better remineralization effect

N. Srinivasan, M. Kavitha, S.C. Loganathan (2010) Compared the remineralization potential of "CPP-ACP" and "CPP-ACP" with 900 ppm fluoride on eroded human enamel in an in vitro study and concluded that "CPP-ACP" and fluoride combination showed higher remineralization potential than "CPP-ACP"

Uy E, Ekambaram M, Lee GHM, Yiu CKY (2019) studied the remineralization Potential of Tooth Mousse Plus and they concluded that it achieved significant remineralization of artificial enamel carious lesions without decreasing the bond strength of brackets

MATERIALS AND METHODOLOGY

MATERIALS AND ARMAMENTARIUM

1. Pre-adjusted edgewise metal brackets of first and second maxillary and mandibular premolar teeth (3M Unitek)
2. 37% phosphoric acid
3. Transbond XT primer (3M Unitek)
4. Transbond XT adhesive (3M Unitek)
5. LED curing lamp (PANAMA CE LED curing light)
6. “CPP-ACPF” (GC Tooth mousse Plus)
7. Universal testing machine (Instron)
8. Stereomicroscope
9. Coca-cola
10. Lipton lemon flavoured ice tea
11. Distilled water
12. 0.1% Thymol solution
13. Digital pH meter

SOURCE OF DATA/ LABORATORY DETAILS:

- The teeth used in this study were selected from patients requiring premolar extraction for orthodontic therapy visiting the Department of Orthodontics and Dentofacial Orthopaedics. The extracted human premolar teeth were collected from the “Department of Oral and Maxillofacial Surgery, KLE Academy of Higher Education & Research, VK Institute of Dental Science, Belagavi”

- The study was done in the “Department of Orthodontics and Dentofacial Orthopaedics, KLE Academy of Higher Education & Research, VK Institute of Dental Science, Belagavi”
- The laboratory procedures were undertaken in “Dr Prabhakar Kore’s Basic Science Research Centre, KLE Academy of Higher Education & Research, VK Institute of Dental Science, Belagavi”
- The shear bond strength of the brackets was assessed at Praj metallurgical lab, Pune
- Specimens were evaluated under the Stereo microscope for checking adhesive remnant index (ARI) at “Department of Oral Pathology, KLE Academy of Higher Education & Research, VK Institute of Dental Science, Belagavi”

INCLUSION CRITERIA:

- “Maxillary or mandibular, first or second premolar teeth”.

EXCLUSION CRITERIA:

- Teeth with visible or detectable caries.
- Teeth with restorations.
- Teeth with hypoplastic lesions, stains, cracks and white spot lesions.
- Teeth with surface defects (erosion, attrition, abrasion).
- Root canal treated teeth.

SAMPLE SIZE ESTIMATION

Sample size estimation based on comparison between two means (Demineralized dentine Vs CPP-ACPF treated demineralized dentine) by an article by Martins LP, et.al., 2018

Formula

$$n = \frac{2s_p^2 \left[z_{1-\alpha/2} + z_{1-\beta} \right]^2}{d^2}$$

$$s_p^2 = \frac{s_1^2 + s_2^2}{2}$$

Where,

- s_1^2 : Standard deviation in the first group
- s_2^2 : Standard deviation in the second group
- d^2 : Mean difference between the samples
- α : Significance level
- $1 - \beta$: Power

The calculation was done as follows:

Standard deviation in group I = 5.92

Standard deviation in group II = 8.83

Mean difference = 23.29

Effect size = 3.15

Alpha Error (%) = 1

Power (%)= 99

sided = 2

Required sample size per group = 5. Since the study involves only in-vitro methods and it was feasible to have a higher sample size, we increased the sample size to 13

per group. Increase in sample size was also done to compensate for any unexpected loss of sample during processing or during measurement of the parameters.

Since the study had two groups and two erosive beverages tested the final sample


13 teeth X 4 groups = 52 teeth

STATISTICAL TEST:

- Kruskal-wallis chi-square

METHODOLOGY:

“Human premolars extracted for orthodontic purposes were used in the study. After extraction the teeth were stored in 0.1% thymol solution to prevent any fungal or bacterial growth.” The teeth were thoroughly cleaned of debris, calculus and soft tissues. The pH of both the beverages were tested before using them. The pH of both the beverages were tested using an electronic pH metre (EUTECH instruments pH meter 510). The pH metre was calibrated using test solutions with a known pH value (Fisher Scientific buffer solution pH 7.0). The pH of Lipton lemon flavoured ice tea was found to be 2.90 and that of Coca-Cola was 2.20. All the groups were treated with the acidic drinks for 90 days, in three sessions of 5 minutes each, during the day. In between the erosion procedure the teeth were kept in distilled water.⁵² selected teeth were randomly divided into four equal groups with respect to the acidic drink used.

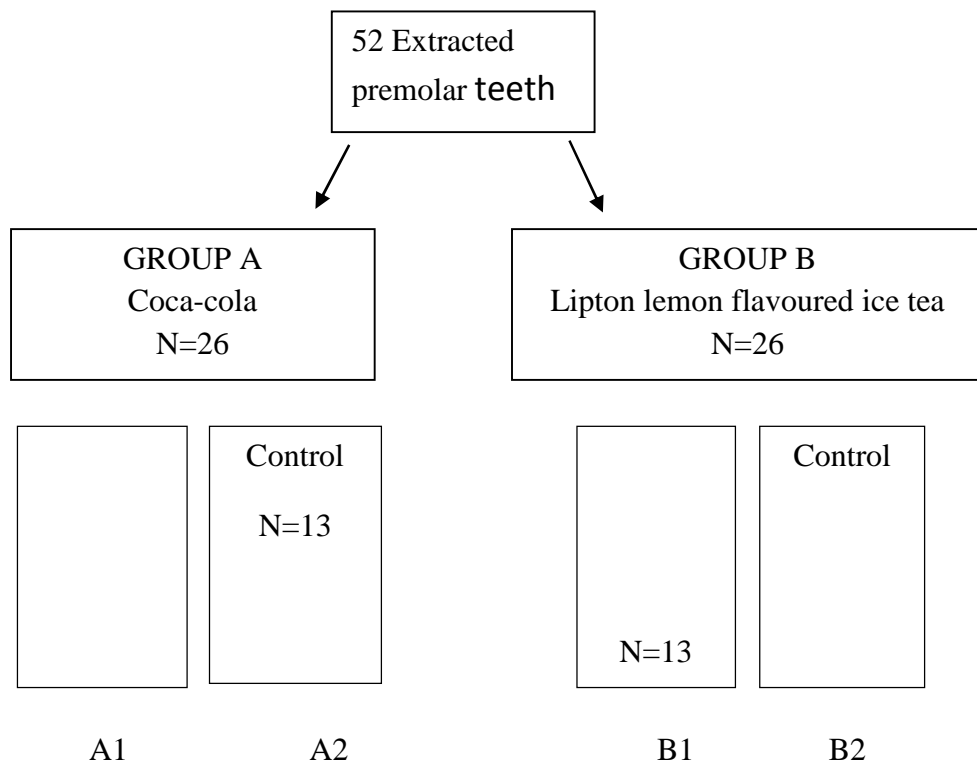

Group A1: The teeth were eroded with Coca-Cola and the enamel was then rubbed with “CCP-ACPF” for 4 mins. The enamel surface was then washed, dried and etched with 37% phosphoric acid for 15 seconds, rinsed with a water spray for 10 seconds and air dried. A thin layer of primer was applied over the etched enamel surface and cured for 20 sec. Metal brackets (3M Unitek) were bonded with etch-and-rinse adhesive system, Transbond XT (3M Unitek) and cured with LED curing gun for 40 sec.

Group A2: The teeth were eroded with Coca-Cola. The enamel surface was then washed, dried and etched with 37% phosphoric acid for 15 seconds, rinsed with a water spray for 10 seconds and air dried. A thin layer of primer was applied over the etched enamel surface and cured for 20 sec. Metal brackets (3M Unitek) were bonded with etch-and-rinse adhesive system, Transbond XT (3M Unitek) and cured with LED curing gun for 40 sec.

Group B1: The teeth were eroded with Lipton lemon flavoured ice tea and the enamel was then rubbed with “CCP-ACPF” for 4 mins. The enamel surface was then washed, dried and etched with 37% phosphoric acid for 15 seconds, rinsed with a water spray for 10 seconds and air dried. A thin layer of primer was applied over the etched enamel surface and cured for 20 sec. Metal brackets (3M Unitek) were bonded with etch-and-rinse adhesive system, Transbond XT (3M Unitek) and cured with LED curing gun for 40 sec.

Group B2: The teeth were eroded with Lipton lemon flavoured ice tea. The enamel surface was then washed, dried and etched with 37% phosphoric acid for 15 seconds, rinsed with a water spray for 10 seconds and air dried. A thin layer of primer was applied over the etched enamel surface and cured for 20 sec. Metal brackets (3M

Unitek) were bonded with etch-and-rinse adhesive system, Transbond XT (3M Unitek) and cured with LED curing gun for 40 sec.

Assessment of shear bond strength

Bonded specimens were stored in distilled water at 37° C for 24 hours, until it was subjected to the shear test. A universal test machine with a load cell of 500 N, operating at a speed of 1mm/min was used for shear bond test. Each specimen was placed with its long axis parallel to the direction of the applied force. The specimens were stressed in an occluso-gingival direction with a uniform crosshead speed of 1mm/min. “The maximum force necessary to debond or initiate bracket failure was recorded in Newton. The SBS in Megapascals (MPa) was computed as a ratio of force in Newton to the surface area of the bracket”.

Adhesive remnant index

After debonding, all the teeth in both the control and experimental groups were analysed using light stereomicroscope at 10 x magnification to determine the failure interface. Any adhesive left on the surface of teeth after debonding was assessed and scored according to the “modified adhesive remnant index.”

“The modified adhesive remnant index” (ARI)^[35]

“ARI scores range from 5 to 1”

“5 - No adherence of composite on enamel”

“4 - Less than 10% of composite remaining on the enamel”

“3 - More than 10% but less than 90% of composite remaining on the enamel”

“2 - More than 90% of composite remaining on the enamel”

“1 - All composite remaining on the enamel, with the impression of the bracket base”



FIGURE 1: GROUP A1 SAMPLES – COCA-COLA, CPP-ACPF TREATED



FIGURE 2: GROUP A2- COCA-COLA, NO PRE-TREATMENT



**FIGURE 3: GROUP B1- LIPTON LEMON FLAVOURED ICE TEA,
CPP-ACPF TREATED**



**FIGURE 4: GROUP B2- LIPTON LEMON FLAVOURED ICE TEA,
NO PRE-TREATMENT**



FIGURE 5:MATERIALS USED



FIGURE 6: BEVERAGES USED FOR CONDITIONING TEETH



FIGURE 7: UNIVERSAL TESTING MACHINE

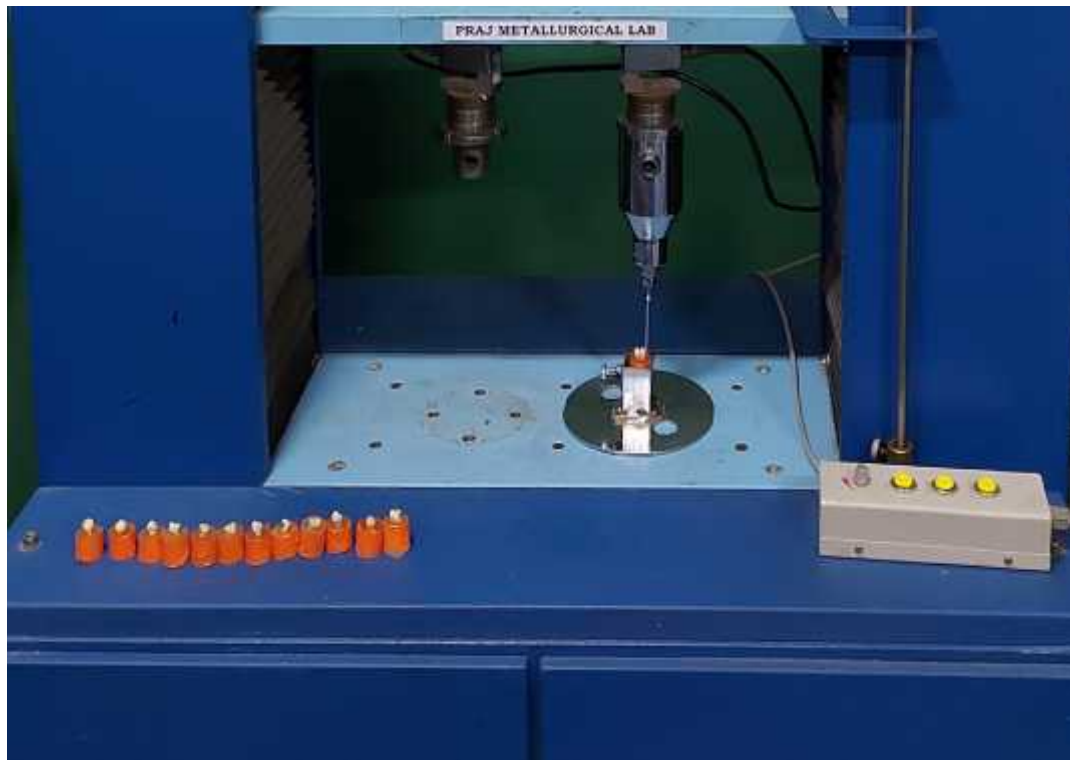


FIGURE 8: SAMPLE SUBJECTED TO LOAD TO MEASURE THE SHEAR BOND STRENGTH



FIGURE 9: CLOSE UP VIEW OF SAMPLE



**FIGURE 10: SAMPLE EVALUATED UNDER STEREO MICROSCOPE TO
MEASURE ARI**

RESULTS

The purpose of this study was to determine whether there is a change in the shear bond strength and adhesive remnant index of teeth eroded by acidic drinks which are pre-treated with a remineralization agent (“CPP-ACPF”) compared to the group without pre-treatment.

INTERPRETATION OF RESULTS

Table 1 shows 52 teeth divided into 4 groups with 13 samples in each group according to the beverage used for erosion and Pre- Treatment procedure

RESULTS OF SHEAR BOND STRENGTH

Table 2: Shows the shear bond strength of each group containing 13 samples each. Shear bond strength was “recorded in Newtons(N) which was converted into Megapascals using following formula”:

$$\text{“Shear bond strength”} = \frac{\text{stress at failure (“N”)}}{\text{Surface area of bracket base}}$$

Mean and standard deviations, minimum, maximum, 25th median, 50th median, 75th median for shear bond strength in each group were calculated.

Group A1 exhibited the maximum median Shear bond strength i.e. 13.23 and group A2 exhibited the lowest i.e. 9.93. But Kruskal-wallis chi square test showed that the difference was not statistically significant.

Graph 1 shows graphical representation of median shear bond strength in Mega Pascals for the groups. Group A1 exhibited the maximum shear bond strength i.e. 13.23.

RESULTS OF ADHESIVE REMNANT INDEX

After debonding, the adhesive left over on the bonded site was assessed and ranked using “Modified Adhesive Remnant Index (ARI)”

Table 3 shows the comparison between groups for ARI index


Graph 2 shows the graphical representation of comparison of ARI index between the groups. The predominant mode of bracket failure for all the groups were such that there was less than 90% of adhesive left on the tooth surface i.e. having Score 3 and 4 which are clinically acceptable. The comparison between the groups were statistically insignificant. None of the groups had score 5 indicating less enamel damage.

TABLE 1: GROUPING OF SAMPLES USED IN THE STUDY

S.NO	GROUP NAME	Beverage used for erosion and Pre- Treatment procedure
1	A1	Coca-Cola, CPP-ACPF treated
2	A2	Coca-Cola, No pre-treatment
3	B1	Lipton lemon flavoured ice tea, CPP-ACPF treated
4	B2	Lipton lemon flavoured ice tea, No pre-treatment


TABLE 2: COMPARISON BETWEEN THE GROUPS FOR SHEAR BOND STRENGTH

Variable	Group	N	Mean	Std. Dev	Min	Max	25th	50th (Median)	75th	Kruskal-Wallis test
N	A1	13	129.35	49.38	77.15	222.55	86.675	119.05	164.525	Kruskal-wallis chi-square: 3.40, df-3, p-value 0.334, Not significant
	A2	13	101.54	40.59	60.1	199.2	73.9	89.35	113	
	B1	13	98.86	22.46	61.75	141.55	84.525	94.85	119.025	
	B2	13	98.70	14.77	76.2	130.8	88.3	96.65	109.925	
Mpa	A1	13	14.39	5.49	8.57	24.73	9.635	13.23	18.29	Kruskal-wallis chi-square: 3.40, df-3, p-value 0.334, Not significant
	A2	13	11.28	4.51	6.68	22.13	8.21	9.93	12.555	
	B1	13	10.98	2.49	6.86	15.73	9.395	10.54	13.225	
	B2	13	10.97	1.64	8.47	14.53	9.81	10.74	12.215	
<p>Interpretation: There was no significant difference between the shear bond strengths as well as ARI values between the groups when compared by Kruskal-wallis test.</p>										

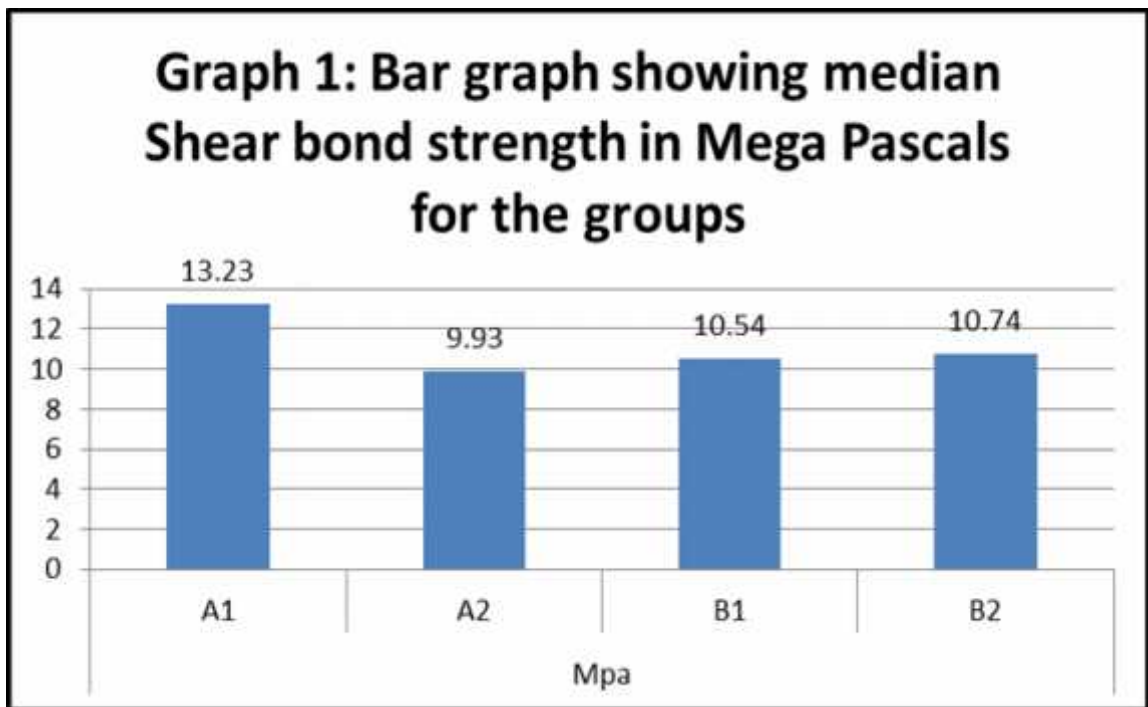

**TABLE 3: COMPARISON BETWEEN THE GROUPS FOR ADHESIVE
REMANT INDEX (ARI)**

Variable	Group	N	Mean	Std. Dev	Min	Max	25th	50th (Median)	75th	Kruskal-Wallis test
ARI	A1	13	3.15	0.69	2	4	3	3	4	Kruskal-wallis chi-square: 3.44, df-3, p-value 0.328, Not significant
	A2	13	3.15	1.07	1	4	2	4	4	
	B1	13	3.38	0.87	1	4	3	4	4	
	B2	13	2.92	0.64	2	4	2.5	3	3	
<p>Interpretation: There was no significant difference between the shear bond strengths as well as ARI values between the groups when compared by Kruskal-wallis test.</p>										

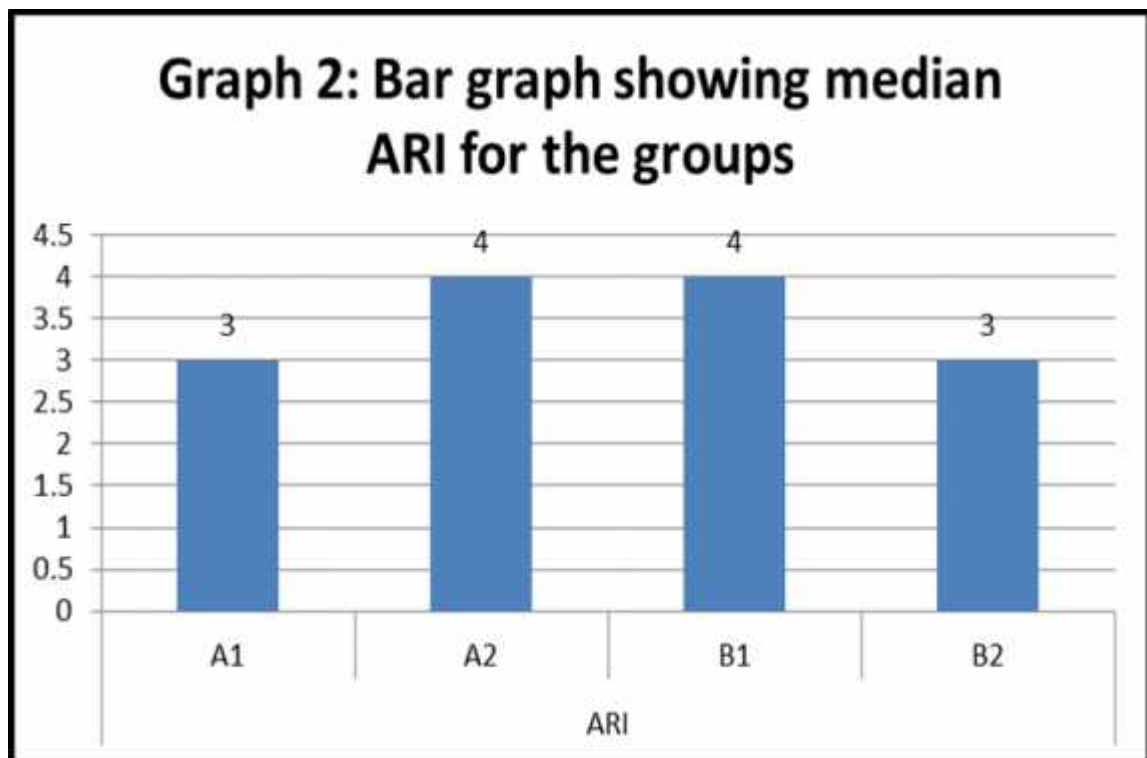

DISCUSSION

“Dental erosion according to Tencate and Imfeld (1996) is the clinical term that is used to describe the physical results of a pathologic, chronic, localized loss of dental hard tissue that is chemically etched away from tooth surface by acid/chelation without bacterial involvement”^[10]

“Dental erosion is also termed as the progressive loss of hard dental tissues by chemical process not involving bacterial action” and it has been reported to be a major cause for tooth surface loss. The three main factors which lead to dental erosion have been discussed under three main classes 1) Dietary 2) Regurgitation 3) Environmental.^[7]

The present study is mainly concerned with dietary causes of tooth loss which is caused by acidic foods and drinks and in particular acidic drinks. Citric acid, phosphoric acid and malic acid are present in most soft drinks and fruit juices which is very commonly consumed by adolescents and children making them a major cause for concern.^[10] Phosphoric acid present in aerated drinks like Coca-cola poses a very high risk for erosion which is also the same acid used for etching.

In addition to soft drinks, consumption of different kinds of tea along with food is becoming very popular these days like green tea, iced tea, and herbal tea because of the added health benefits they report to have. As most of these are consumed without milk various fruit flavours are added to them to make them more palatable like lemon, apple, peach etc. which makes it more acidic compared to the regular tea as it contains “hydroxyl organic acids, such as citric, malic, and oxalic acid (Hughes et al.)”.^[1]

In a study done by Phelan and Rees they had found that Lipton lemon flavoured ice tea and lift instant tea had high neutralisable acidity levels, both of these products contain citric acid and Vitamin C (ascorbic acid), which are strong organic acids because of which Lipton iced tea produced high amounts of erosion.^[36]

According to a recent systematic review by Chan et al the risk factors which showed an association with dental erosion according to their severity were “carbonated drinks (51%), fruit juice (29%), sports/energy drinks (29%), and tea (29%) for beverages; confectionery (43%), sauces (43%), citrus fruits (26%), and vinegar/pickles (26%) for food; and a swishing drinking habit/retaining drinks in the mouth (41%) and consumption of acidic drinks/food/beverages at bedtime (29%) for dietary habits.”^[8]

“Dissolution of enamel occurs when the pH falls below the pH of 5.5 which is reported to be the critical limit for enamel demineralization”.^[3] The pH of Coca-cola was found to be 2.2 initially and it fell to 2.10 after 5 minutes. The pH of Lipton lemon iced tea was found to be 2.92 initially and fell to 2.90 5 minutes later.

Saliva is the main protective mechanism present in the oral cavity against acidic substances which acts as a buffering agent, aids in the formation of acquired enamel pellicle and also provides a supersaturated solution of calcium phosphate. A fall in pH increases the salivary secretion buffering the acidic substance, the fluoride ions in the saliva also inhibits demineralization.^[11] Even though protective mechanisms are there continuous usage of these beverages or holding and swishing it in the oral cavity is detrimental to the tooth structure.

Debonding of brackets during the treatment is a commonly encountered problem and even though it could be because of a wide variety of reasons one of them

is erosive damage to the tooth surface itself causing a reduction in bond strength^{[6], [9]}
[8] had all come to the same conclusion that teeth eroded by various acidic drinks statistically significantly reduces the bond strength.

To reduce this the best way would be the elimination of the cause, which is avoiding acidic drinks and food during the treatment. Since this is not always possible as it is dependent on patient cooperation, another way is the prevention of erosion or reducing the extent of the lesion by various methods “which requires calcium, phosphate and fluoride”. “Casein phosphopeptide–amorphous calcium phosphate (CPP-ACP) with fluoride sold under the brand name GC Tooth Mousse plus has been reported to reduce the demineralization process for up to 4 weeks and aid in the remineralization process for up to 12 weeks after the application”.^[6]

Various studies have been done to see the effect of “CPP-ACPF” on demineralized teeth and all of them had a positive result where the shear bond strength had improved compared to the untreated control group^{[15], [24], [25], [27], [28], [30], [32]}

In the present study the teeth were eroded by two acidic drinks i.e. Coca-cola and Lipton lemon flavoured ice tea which were later treated with “CPP-ACPF” before acid etching and bonding to determine if it reduced the erosive lesions and whether it could increase the bond strength of the eroded teeth as observed in the demineralized teeth.

“Reynolds suggested that a minimum bond strength of 6 to 8 MPa was adequate for most clinical orthodontic needs. These bond strengths are considered able to withstand masticatory and orthodontic forces”.^[34] In the current study we saw that the minimum bond strength obtained even in the control group was 6.86 which is

clinically acceptable indicating that if the erosion is not extensive bonding can be done without any Pre-treatment.

While comparing the median bond strength between group A1 and A2, group A1 had a higher bond strength i.e. “CPP-ACPF” treated group exhibited a higher median bond strength compared to the control group even though it is statistically insignificant suggesting that when the teeth are highly eroded “CPP-ACPF” containing tooth pastes can be given to patients for remineralization without compromising the bond strength and it can aid in increasing the bond strength in teeth which are eroded by aerated soft drinks.

In the Lipton iced tea treated groups i.e. B1 and B2, the median bond strength of B1 group had not increased compared to B2, this could be because the citric acid in the drink may “act as a chelator capable of binding calcium from enamel or dentin creating a higher degree of undersaturation”^[10] and indicating that the calcium and phosphate in the tooth paste might not have been sufficient to cover up the undersaturation effect.

In the present study the main objective was to see if the bond strength could be increased before bonding as we would have some control over the consumption of the beverage after bonding by advising the patients not to consume the drink after starting the treatment. One of the reasons why the bond strength did not decrease to a larger extent compared to the other studies which were eroded by soft drinks, could be because in this study the beverage treatment was done before bonding, causing only some damage to the enamel surface unlike in the other studies where there would be damage to the enamel and also the adhesive causing softening of the enamel and adhesive reducing the bond strength to a much larger extent.

Most of the specimens in the study gave an ARI score of 3 and 4 similar to the results obtained by Ulusoy et al^[1] this indicates that some amount of adhesive was always left on the teeth indicating that bond failure mostly happened between the enamel adhesive interface reducing the clean-up time and reducing the chances of enamel fracture. This also indicates that adhesive-bracket bond was stronger compared to enamel-adhesive bond. The adhesive left on the enamel can later be removed with tungsten carbide bur followed by finishing.

LIMITATION OF THE STUDY

- The main limitation of the study was that it was done In-Vitro which fails to simulate the oral conditions. “CPP-ACPF” acts better when combined with saliva in the oral conditions suggesting the need for an In-Vivo study. Conducting this study In-Vivo would have been difficult as we would have needed patients who had been consuming soft drinks on a constant basis with eroded teeth which are indicated for extraction.
- Irrespective of these limitations the findings of the current study show that when the teeth are highly eroded we could ask the patients to use tooth pastes containing remineralization agents like “CPP-ACPF” without further compromising the bond strength and in fact it might have a beneficial effect on the bond strength of teeth which are eroded by aerated soft drinks as seen in the current study.

CONCLUSIONS

1. Application of remineralization agents like “CPP-ACPF” on teeth eroded by aerated soft drinks, increased the median shear bond strength.
2. “CPP-ACPF” pre-treatment did not increase the SBS of teeth eroded by Lipton lemon flavoured ice tea.
3. Irrespective of the acidic beverage used for erosion, or the enamel pre-treatment with “CPP-ACPF”, statistically significant difference was not seen in the SBS between the groups which suggests the need for further clinical studies to find the effectiveness of the remineralization procedure.
4. Bond failure of brackets in all the group was at enamel-adhesive interface leaving some residue on the enamel surface.

SUMMARY

The consumption of acidic drinks like various soft drinks, tea, energy drinks have increased in the recent past. When the pH of the medium is below 5.5 i.e. critical limit for enamel demineralization, it has been reported to cause loss of tooth surface and erosion. Studies have shown that eroded teeth have lower bond strength. In the present study the main aim was to find whether there would be any effect on the bond strength of the eroded teeth if a remineralization agent containing tooth paste like GC tooth mousse was used which contains “CPP-ACPF”.

The result showed that using “CPP-ACPF” the median bond strength in the group of teeth eroded by Coca-cola had increased even though not statistically significant. The bond strength of Lipton lemon flavoured ice tea group did not have any effect, the bond strength did not decrease or increase. Clinically acceptable bond strengths were seen in all the groups by which depicts that if the erosion in the teeth are not too extensive, bonding can be done without any pre-treatment procedures and if it is extensive remineralization agents like “CPP-ACPF” could be used where we could get a beneficial effect on the surface hardness of the enamel as reported by previous studies, and as it does not further decrease the bond strength it can be used before bonding the teeth. Bond failure of brackets as assessed by adhesive remnant index in all the groups were at enamel-adhesive interface leaving some residue on the enamel surface, which is clinically acceptable.

BIBLIOGRAPHY

1. **Ulusoy Ç, Müjdeci A, Gökay O.** The effect of herbal teas on the shear bond strength of orthodontic brackets. *The European Journal of Orthodontics*. 2009 Aug 1;31(4):385-9.
2. **Carvalho TS, Lussi A.** Acidic Beverages and Foods Associated with Dental Erosion and Erosive Tooth Wear. In *The Impact of Nutrition and Diet on Oral Health 2020* (Vol. 28, pp. 91-98). Karger Publishers.
3. **Navarro R, Vicente A, Ortiz AJ, Bravo LA.** The effects of two soft drinks on bond strength, bracket microleakage, and adhesive remnant on intact and sealed enamel. *The European Journal of Orthodontics*. 2011 Feb 1;33(1):60-5.
4. **Pasha A, Sindhu D, Nayak RS, Mamatha J, Chaitra KR, Vishwakarma S.** The effect of two soft drinks on bracket bond strength and on intact and sealed enamel: an in vitro study. *Journal of international oral health: JIOH*. 2015;7(Suppl 2):26.
5. **Panich M, Poolthong S.** The effect of casein phosphopeptide–amorphous calcium phosphate and a cola soft drink on in vitro enamel hardness. *The Journal of the American Dental Association*. 2009 Apr 1;140(4):455-60.
6. **Abufarwa M, Noureldin A, Campbell PM, Buschang PH.** The longevity of casein phosphopeptide–amorphous calcium phosphate fluoride varnish's preventative effects: Assessment of white spot lesion formation. *The Angle Orthodontist*. 2019 Jan;89(1):10-5.
7. **Kelleher M, Bishop K.** Tooth surface loss: an overview. *British Dental Journal*. 1999 Jan;186(2):61-6.

8. **Chan AS, Tran TT, Hsu YH, Liu SY, Kroon J.** A systematic review of dietary acids and habits on dental erosion in adolescents. *International Journal of Paediatric Dentistry*. 2020 Apr 4.
9. **Hasheminejad N, Mohammadi TM, Mahmoodi MR, Barkam M, Shahravan A.** The association between beverage consumption pattern and dental problems in Iranian adolescents: a cross sectional study. *BMC Oral Health*. 2020 Dec;20(1):1-9.
10. **Rajeev G, Lewis AJ.** A time based objective evaluation of the erosive effects of various beverages on enamel and cementum of deciduous and permanent teeth. *Journal of Clinical and Experimental Dentistry*. 2020 Jan;12(1):e1.
11. **Dixon M, Jones Y, Mackie IE, Derwent SK.** Mandibular incisal edge demineralization and caries associated with Twin Block appliance design. *Journal of orthodontics*. 2005 Mar;32(1):3-10.
12. **Casas-Apayco LC, Dreibi VM, Hipolito AC, Graeff MS, Rios D, Magalhaes AC, Buzalaf MA, Wang L.** Erosive cola-based drinks affect the bonding to enamel surface: an in vitro study. *Journal of Applied Oral Science*. 2014 Oct;22(5):434-41.
13. **Çehreli SB, ar Ç, Polat-Özsoy Ö, Ünver B, Özsoy S.** Effects of a fluoride-containing casein phosphopeptide–amorphous calcium phosphate complex on the shear bond strength of orthodontic brackets. *The European Journal of Orthodontics*. 2012 Apr 1;34(2):193-7
14. **Balakrishnan A, Jonathan R, Benin P, Kumar A.** Evaluation to determine the caries remineralization potential of three dentifrices: An in vitro study. *Journal of conservative dentistry: JCD*. 2013 Jul;16(4):375.



15. **Barbosa-Martins LF, Sousa JP, Alves LA, Davies RP, Puppini-Rontanti RM.** Biomimetic mineralizing agents recover the micro tensile bond strength of demineralized dentin. *Materials*. 2018 Sep;11(9):1733.
16. **Reynolds EC.** Remineralization of enamel subsurface lesions by casein phosphopeptide-stabilized calcium phosphate solutions. *Journal of dental research*. 1997 Sep;76(9):1587-95.
17. **Cate JM.** Current concepts on the theories of the mechanism of action of fluoride. *Acta Odontologica Scandinavica*. 1999 Jan 1;57(6):325-9.
18. **Somani R, Jaidka S, Singh DJ, Arora V.** Remineralizing potential of various agents on dental erosion. *Journal of oral biology and craniofacial research*. 2014 May 1;4(2):104-8.
19. **Gokkaya B, Ozbek N, Guler Z, Akman S, Sarac AS, Kargul B.** Effect of a Single Application of CPP-ACPF Varnish on the Prevention of Erosive Tooth Wear: An AAS, AFM and SMH Study. *Oral Health Prev Dent*. 2020 Apr 1;18:311-8.
20. **Keçik D, Çehrelî SB, ar Ç, Ünver B.** Effect of acidulated phosphate fluoride and casein phosphopeptide–amorphous calcium phosphate application on shear bond strength of orthodontic brackets. *The Angle Orthodontist*. 2008 Jan;78(1):129-33.
21. **Xiaojun D, Jing L, Xuehua G, Hong R, Youcheng Y, Zhangyu G, Sun J.** Effects of CPP-ACP paste on the shear bond strength of orthodontic brackets. *The Angle Orthodontist*. 2009 Sep;79(5):945-50.
22. **Tabrizi A, Cakirer B.** A comparative evaluation of casein phosphopeptide-amorphous calcium phosphate and fluoride on the shear bond strength of

- orthodontic brackets. *The European Journal of Orthodontics*. 2011 Jun 1;33(3):282-7.
23. **Uysal T, Baysal A, Uysal B, Aydınbelge M, Al-Qunaian T.** Do fluoride and casein phosphopeptide–amorphous calcium phosphate affect shear bond strength of orthodontic brackets bonded to a demineralized enamel surface?. *The Angle Orthodontist*. 2011 May;81(3):490-5.
24. **Baysal A, Uysal T.** Do enamel microabrasion and casein phosphopeptide–amorphous calcium phosphate affect shear bond strength of orthodontic brackets bonded to a demineralized enamel surface?. *The Angle Orthodontist*. 2012 Jan;82(1):36-41.
25. **Ekizer A, Zorba YO, Uysal T, Ayrikcila S.** Effects of demineralization-inhibition procedures on the bond strength of brackets bonded to demineralized enamel surface. *The Korean Journal of Orthodontics*. 2012 Feb 1;42(1):17-22.
26. **Soares R, De Ataíde ID, Fernandes M, Lambor R.** Assessment of enamel remineralisation after treatment with four different remineralising agents: A Scanning Electron Microscopy (SEM) Study. *Journal of clinical and diagnostic research: JCDR*. 2017 Apr;11(4):ZC136.
27. **Manoharan V, Kumar RK, Sivanraj AK, Arumugam SB.** Comparative evaluation of remineralization potential of casein phosphopeptide-amorphous calcium fluoride phosphate and novamin on artificially demineralized human enamel: An In vitro study. *Contemporary clinical dentistry*. 2018 Jun;9(Suppl 1):S58.

28. **Baka ZM, Akin M, Ileri Z, Basciftci FA.** Effects of remineralization procedures on shear bond strengths of brackets bonded to demineralized enamel surfaces with self-etch systems. *The Angle Orthodontist*. 2016 Jul;86(4):661-7.
29. **Garry AP, Flannigan NL, Cooper L, Komarov G, Burnside G, Higham SM.** A randomised controlled trial to investigate the remineralising potential of Tooth Mousse™ in orthodontic patients. *Journal of orthodontics*. 2017 Sep;44(3):147-56.
30. **Nahidh M.** The effects of various beverages on the shear bond strength of light-cured orthodontic composite (An in vitro comparative study). *Journal of baghdad college of dentistry*. 2014;26(3):144-8.
31. **Srinivasan N, Kavitha M, Loganathan SC.** Comparison of the remineralization potential of CPP–ACP and CPP–ACP with 900 ppm fluoride on eroded human enamel: an in situ study. *Archives of oral biology*. 2010 Jul 1;55(7):541-4.
32. **Uy E, Ekambaram M, Lee GH, Yiu CK.** Remineralization potential of calcium and phosphate-based agents and their effects on bonding of orthodontic brackets. *The journal of adhesive dentistry*. 2019 May 1;21(3):219-28.
33. **Hamasha AA, Zawaideh FI, Al-Hadithy RT.** Risk indicators associated with dental erosion among Jordanian school children aged 12–14 years of age. *International Journal of Paediatric Dentistry*. 2014 Jan;24(1):56-68
34. **Reynolds IR.** A review of direct orthodontic bonding. *British journal of orthodontics*. 1975 Jul 1;2(3):171-8.

35. **Olsen ME, Bishara SE, Damon P, Jakobsen JR.** Evaluation of Scotchbond Multipurpose and maleic acid as alternative methods of bonding orthodontic brackets. *American journal of orthodontics and dentofacial orthopedics*. 1997 May 1;111(5):498-501.
36. **Phelan J, Rees J.** The erosive potential of some herbal teas. *Journal of dentistry*. 2003 May 1;31(4):241-6.

ANNEXURE – I
ETHICAL CLEARANCE

	<p>Research and Ethics Committee KLE V K INSTITUTE OF DENTAL SCIENCES KLE University</p> <p>Accredited 'A' Grade by NAAC Placed in Category 'A' by MHRD (Govt)</p> <p>Nehru Nagar, Belagavi - 590 010, Karnataka State</p> <p>☎: 0831-2470362 Web: http://www.kledental-bgm.edu.in FAX: 0831-2470640 E-mail: principal@kledental-bgm.edu.in</p>	
SI. No. : 1223		
CERTIFICATE		
<i>This is to Certify that the synopsis titled</i>		
<p><i>Effects of a fluoride containing casein phosphopeptide amorphous calcium phosphate complex on shear bond strength and adhesive remnant index of teeth eroded by different beverages: An in vitro study. Submitted by</i></p> <p><i>Dr. Ann Binay</i> <i>P. G. Student /</i></p> <p><i>Staff, Guided by Dr. Rohan S Hattarki from Department of Orthodontics & Dentofacial orthopedics has been critically evaluated by committee members and granted ethical clearance to conduct the above mentioned study</i></p>		
<p>Date : <i>24/06/2019</i></p>		
<p>Member Secretary Research and Ethical Committee KLEVK Institute of Dental Sciences Belagavi</p>	<p>Chairman Research and Ethical Committee KLEVK Institute of Dental Sciences Belagavi</p>	

ANNEXURE – II
DATA ENTRY SHEET

S.NO.	SAMPLE NO.	GROUP							
		A1		A2		B1		B2	
		(N)	(Mpa)	(N)	(Mpa)	(N)	(Mpa)	(N)	(Mpa)
1	1	155.7	17.3	105.6	11.73	61.75	6.86	90.1	10.01
2	2	207.1	23	60.1	6.68	88.3	9.81	102.6	11.39
3	3	119.1	13.23	89.35	9.93	84.2	9.36	80	8.89
4	4	86	9.56	68.95	7.66	120.1	13.34	111.2	12.35
5	5	78.6	8.73	65.25	7.25	101.8	11.31	86.5	9.61
6	6	87.35	9.71	86.6	9.62	121.2	13.46	109.5	12.16
7	7	91.9	10.21	167.9	18.65	84.85	9.43	130.8	14.53
8	8	173.4	19.28	78.85	8.76	90.65	10.07	102.6	11.4
9	9	135.8	15.31	92.65	10.29	141.6	15.73	96.65	10.74
10	10	97.55	10.84	79.65	8.85	69.9	7.77	110.4	12.27
11	11	222.6	24.73	110.3	12.25	94.85	10.54	76.2	8.47
12	12	77.15	8.57	199.2	22.13	108.1	12.01	95.5	10.61
13	13	149.5	16.61	115.8	12.86	118	13.11	91.17	10.13

S.NO.	SAMPLE NO.	GROUP			
		A1	A2	B1	B2
1	1	3	4	3	2
2	2	4	4	4	3
3	3	2	2	1	3
4	4	3	2	3	2
5	5	4	1	4	3
6	6	4	4	3	2
7	7	3	4	3	3
8	8	3	2	4	3
9	9	2	4	4	4
10	10	3	3	3	3
11	11	3	4	4	4
12	12	3	3	4	3
13	13	4	4	4	3